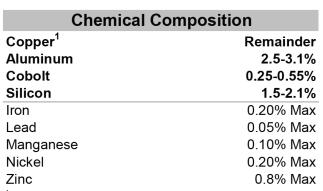


Coronze, or Alloy C638 is a high strength, cost effective, cobalt-modified aluminum silicon bronze which was developed for its corrosion resistant properties, particularly its oxidation resistance at elevated temperatures. A number of superior qualities, including surface characteristics, formability, strength and conductivity, make C638 an excellent choice for use in a wide range of applications including electrical connectors and spring contacts.



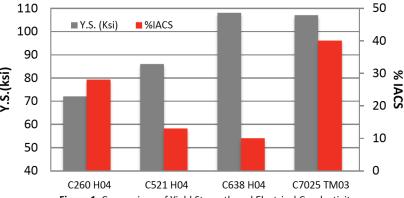


Figure 1: Comparison of Yield Strength and Electrical Conductivity performance of select high strength connector materials

1 Cu + Named	Elements,	99.5%	min
--------------	-----------	-------	-----

Physical Properties					
	English Units	Metric Units			
Density	0.299 lb/in ³ @ 68°F	8.28 g/cm ³			
Thermal Conductivity	22.0 BTU-ft/ft ² -hr-°F	38 W/m°K			
Electrical Resistivity	104 ohm circ mils/ft	17.4 microhm-cm			
Electrical Conductivity (annealed)	10% IACS*	0.058 megamho/cm			
Modulus of Elasticity	16,700,000 psi	115 kN/mm ²			
Thermal Capacity(Specific Heat)	0.090 Btu/lb/F° @ 68°F	377.1 J/kg ⋅ ºC @ 20ºC			
Coeff. Of Thermal Expansion	_				
68-572°F (20-300°C)	9.5 PPM/°F	17.1 PPM/°C			
*International Annealed Copper Standard	'				

Mechanical Properties										
Temper ¹	Tensile Strength		Yield Strength ²		% Elongation ²	Typical 90° Bend Formability				
	ksi	N/mm ²	ksi	N/mm ²		GW/BW ³				
Annealed	77-87	530-600	56	385	33	-	_			
1/4 Hard	90-102	620-705	82	565	16	0.5	1.5			
1/2 Hard	100-112	690-770	93	640	10	8.0	2.0			
3/4 Hard	105-117	725-805	99	685	7	1.0	2.5			
Hard	114-126	785-870	108	745	4	1.5	3.5			
Extra Hard	118-130	815-895	112	770	3	2.3	4.5			
Spring	123-134	850-925	116	800	2	3.0	7.0			
Extra Spring	130 min	895 min	119 min	820 min	2 Max					

¹ Mechanical properties subject to change. All tempers listed are made to a Tensile Strength specification unless otherwise noted.

² Nominal Values ³ DATA FOR REFERENCE ONLY. R/T = Bend Radius/Material Thickness <0.016" (0.4mm) thick, 11/16 (17.5mm) wide.